



中国认可
国际互认
检测
TESTING
CNAS L6478



TEST REPORT

Report No. : WTF20F05031544C

Applicant : Mid Ocean Brands B.V.

Address : 7/F., Kings Tower, 111 King Lam Street, Cheung Sha Wan, Kowloon, Hong Kong

Manufacturer : 111587

Sample Name : Backpack in RPET w/COB light

Model No. : MO9969

Sample Receiving Date : 2020-05-27

Testing Period : 2020-05-27 to 2020-06-03

Date of Issue : 2020-06-04

Test Result : Please refer to next page (s)

Remarks:

The results shown in this test report refer only to the sample(s) tested; this test report cannot be reproduced, except in full, without prior written permission of the company. The report would be invalid without specific stamp of test institute and the signatures of compiler and approver.
If the report is not stamped with the accreditation recognized seal, it will only be used for scientific research, education, and internal quality control activities, and is not used for the purpose of issuing supporting data to the society.

Prepared By:

Waltek Services (Foshan) Co., Ltd.

Address: No.13-19, 2/F., 2nd Building, Sunlink International Machinery City,
Chencun, Shunde District, Foshan, Guangdong, China

Tel:+86-757-23811398 Fax:+86-757-23811381 E-mail:info@waltek.com.cn

Compiled by:

Humour.Wu

Humour.Wu / Project Engineer

Approved by:



Swing Liang

Swing.Liang / Technical Manager



- Test Requested**..... : In accordance with the RoHS Directive 2011/65/EU and its amendment (EU) No. 2015/863.
- Test Method** :
 - 1) With Reference to IEC 62321-2:2013, disassembly, disjunction and mechanical sample preparation
 - 2) With Reference to IEC 62321-3-1:2013, screening - Lead, mercury, cadmium, total chromium and total bromine by X-ray fluorescence spectrometry
 - 3) With reference to IEC 62321-4:2013+AMD1:2017 CSV, determination of Mercury by ICP-OES
 - 4) With reference to IEC 62321-5:2013, determination of Lead and Cadmium by ICP-OES
 - 5) With reference to IEC 62321-7-2: 2017 and IEC 62321-7-1: 2015, determination of Hexavalent Chromium by UV-Vis
 - 6) With reference to IEC 62321-6:2015, determination of PBBs and PBDEs by GC-MS
 - 7) With reference to IEC 62321-8:2017, determination of Phthalates content by GC-MS.
- Test Conclusion**..... : **Pass** (Based on the performed tests on the submitted samples, the results comply with the RoHS Directive 2011/65/EU and its amendment (EU) No. 2015/863)



WALTEK

**Test Results:****1. Lead, Mercury, Cadmium, Hexavalent Chromium, PBBs and PBDEs**

Part No.	Part Description	Result of XRF					Result of Wet Chemical Testing (mg/kg)
		Cd	Pb	Hg	Cr	Br	
1	Black plastic sheet with silvery coating	BL	BL	BL	BL	BL	NA
2	Blue plastic holder	BL	BL	BL	BL	BL	NA
3	Black soft plastic sheet	BL	BL	BL	BL	BL	NA
4	Transparent plastic sheet	BL	BL	BL	BL	BL	NA
5	Black soft plastic sheet	BL	BL	BL	BL	BL	NA
6	Transparent plastic adhesive label with black printing	BL	BL	BL	BL	BL	NA
7	Semi-transparent glue	BL	BL	BL	BL	BL	NA
8	Green PCB	BL	BL	BL	BL	IN	PBBs : ND PBDEs : ND
9	Silvery metal spring	BL	BL	BL	BL	BL	NA
10	Chip LED	BL	BL	BL	BL	BL	NA
11	Chip IC	BL	BL	BL	BL	BL	NA
12	Chip capacitor	BL	BL	BL	BL	BL	NA
13	Chip diode	BL	BL	BL	BL	BL	NA
14	Chip audion	BL	BL	BL	BL	IN	PBBs : ND PBDEs : ND
15	Chip resistor	BL	*OL	BL	BL	BL	NA
16	Golden metal key of button	BL	BL	BL	BL	BL	NA
17	Silvery metal shell of button	BL	BL	BL	IN	BL	Cr ⁶⁺ : Negative
18	Silvery metal sheet of button	BL	BL	BL	IN	BL	Cr ⁶⁺ : Negative
19	Silvery metal pin of button	BL	BL	BL	BL	BL	NA



Part No.	Part Description	Result of XRF					Result of Wet Chemical Testing (mg/kg)
		Cd	Pb	Hg	Cr	Br	
20	Yellow plastic adhesive label of button	BL	BL	BL	BL	BL	NA
21	Black plastic base of button	BL	BL	BL	BL	BL	NA
22	Chip resistor	BL	*OL	BL	BL	BL	NA
23	Solder	BL	BL	BL	BL	BL	NA

Remark:

- (1) Results are obtained by EDXRF for primary screening, and further chemical testing by ICP (for Cd, Pb, Hg), UV-VIS (for Cr⁶⁺) and GC-MS (for PBBs, PBDEs) is recommended to be performed, if the concentration exceeds the below warning value according to IEC 62321-3-1: 2013 (unit: mg/kg)

Element	Polymer	Metal	Composite Materials
Cd	BL ≤ (70-3σ) < IN < (130+3σ) ≤ OL	BL ≤ (70-3σ) < IN < (130+3σ) ≤ OL	LOD < IN < (150+3σ) ≤ OL
Pb	BL ≤ (700-3σ) < IN < (1300+3σ) ≤ OL	BL ≤ (700-3σ) < IN < (1300+3σ) ≤ OL	BL ≤ (500-3σ) < IN < (1500+3σ) ≤ OL
Hg	BL ≤ (700-3σ) < IN < (1300+3σ) ≤ OL	BL ≤ (700-3σ) < IN < (1300+3σ) ≤ OL	BL ≤ (500-3σ) < IN < (1500+3σ) ≤ OL
Cr	BL ≤ (700-3σ) < IN	BL ≤ (700-3σ) < IN	BL ≤ (500-3σ) < IN
Br	BL ≤ (300-3σ) < IN	--	BL ≤ (250-3σ) < IN

BL= Below Limit OL= Over Limit LOD = Limit of Detection -- = Not Regulated

- (2) "IN" expresses the inconclusive region, and further chemical testing to confirm whether it complies with the requirement of RoHS Directive.
- (3) The XRF screening test for RoHS elements – the reading may be different to the actual content in the sample be of non-uniformity composition.
- (4) mg / kg =milligram per kilogram=ppm, μg/cm²= Micrograms per square centimetre.
- (5) ND = Not Detected or lower than limit of quantitation.
- (6) NA = Not Applicable, as the XRF screening test result was below the limit or as the XRF screening directly determine that test result was over the limit, it was not need to conduct the wet chemical testing.
- (7) LOQ = Limit of quantitation.

Test Items	Pb	Cd	Hg	Cr ⁶⁺		PBB	PBDE
Units	mg/kg	mg/kg	mg/kg	mg/kg	μg/cm ²	mg/kg	mg/kg
LOQ	2	2	2	8	0.1	5	5

The LOQ for single compound of PBBs and PBDEs is 5mg/kg, LOQ of Cr⁶⁺ for polymer and composite sample is 8mg/kg and LOQ of Cr⁶⁺ for metal sample is 0.1μg/cm².



(8) RoHS Requirement

Restricted Substances	Limits
Cadmium (Cd)	0.01% (100 mg/kg)
Lead (Pb)	0.1% (1000 mg/kg)
Mercury (Hg)	0.1% (1000 mg/kg)
Chromium (VI) (Cr ⁶⁺)	0.1% (1000 mg/kg)
Polybrominated Biphenyls (PBBs)	0.1% (1000 mg/kg)
Polybrominated Diphenyl Ethers (PBDEs)	0.1% (1000 mg/kg)

(9) According to IEC 62321-7-1:2015, determined of Cr⁶⁺ on metal sample by boiling water extraction test method, and result is shown as Positive/Negative.

Boiling water extraction:

Negative = Absence of Cr⁶⁺ coating, the detected concentration in boiling water extraction solution is less than 0.10ug/cm².

Positive = Presence of Cr⁶⁺ coating, the detected concentration in boiling water extraction solution is greater than 0.13ug/cm².

Information on storage conditions and production date of the tested sample is unavailable and thus Cr⁶⁺ results represent status of the sample at the time of testing.

(10) Abbreviation:

“Pb” denotes Lead, “Cd” denotes Cadmium, “Hg” denotes Mercury, “Cr” denotes Chromium, “Cr (VI)” denotes Hexavalent Chromium, “Br” denotes Bromine, “PBBs” denotes Total Polybrominated Biphenyls, “PBDEs” denotes Total Polybrominated Diphenyl Ethers.

(11)* = According to the declaration from client, the source of lead in test sample is from the glass or ceramic material of that electronic component which is exempted by Directive 2011/65/EU.

WALTEK



2. Phthalates:

Serial No.	Part No.	Result (mg/kg)			
		DBP	BBP	DEHP	DIBP
T01	1+2+4 [△]	136	<50	<50	<50
T02	3	<50	<50	<50	<50
T03	5	<50	<50	<50	<50
T04	6	<50	<50	110	<50
T05	7	<50	<50	<50	<50
T06	8+15+22 [△]	<50	<50	<50	<50
T07	10+11+12+13+14 [△]	<50	<50	<50	<50
T08	20	<50	<50	<50	<50
T09	21	<50	<50	<50	<50

Note:

- (1) "<" = less than
- (2) mg/kg = milligram per kilogram= ppm
- (3) Abbreviation:
"DBP" denotes Dibutyl phthalate, "BBP" denotes Benzyl butyl phthalate (BBP), "DEHP" denotes Bis(2-ethylhexyl)-phthalate, "DIBP" denotes Diisobutyl phthalate, "PHT" denotes Phthalates.

- (4) RoHS requirement


Restricted Substances	Limits
Dibutyl phthalate (DBP)	0.1% (1000 mg/kg)
Benzyl butyl phthalate (BBP)	0.1% (1000 mg/kg)
Di(2-ethylhexyl) phthalate (DEHP)	0.1% (1000 mg/kg)
Di-iso-butyl phthalate (DIBP)	0.1% (1000 mg/kg)

- (5) "△"= As client's requirement, the testing was conducted based on mixed components. Results are calculated by the minimum weight of mixed components.

WALTEK




Measurement Flowchart:

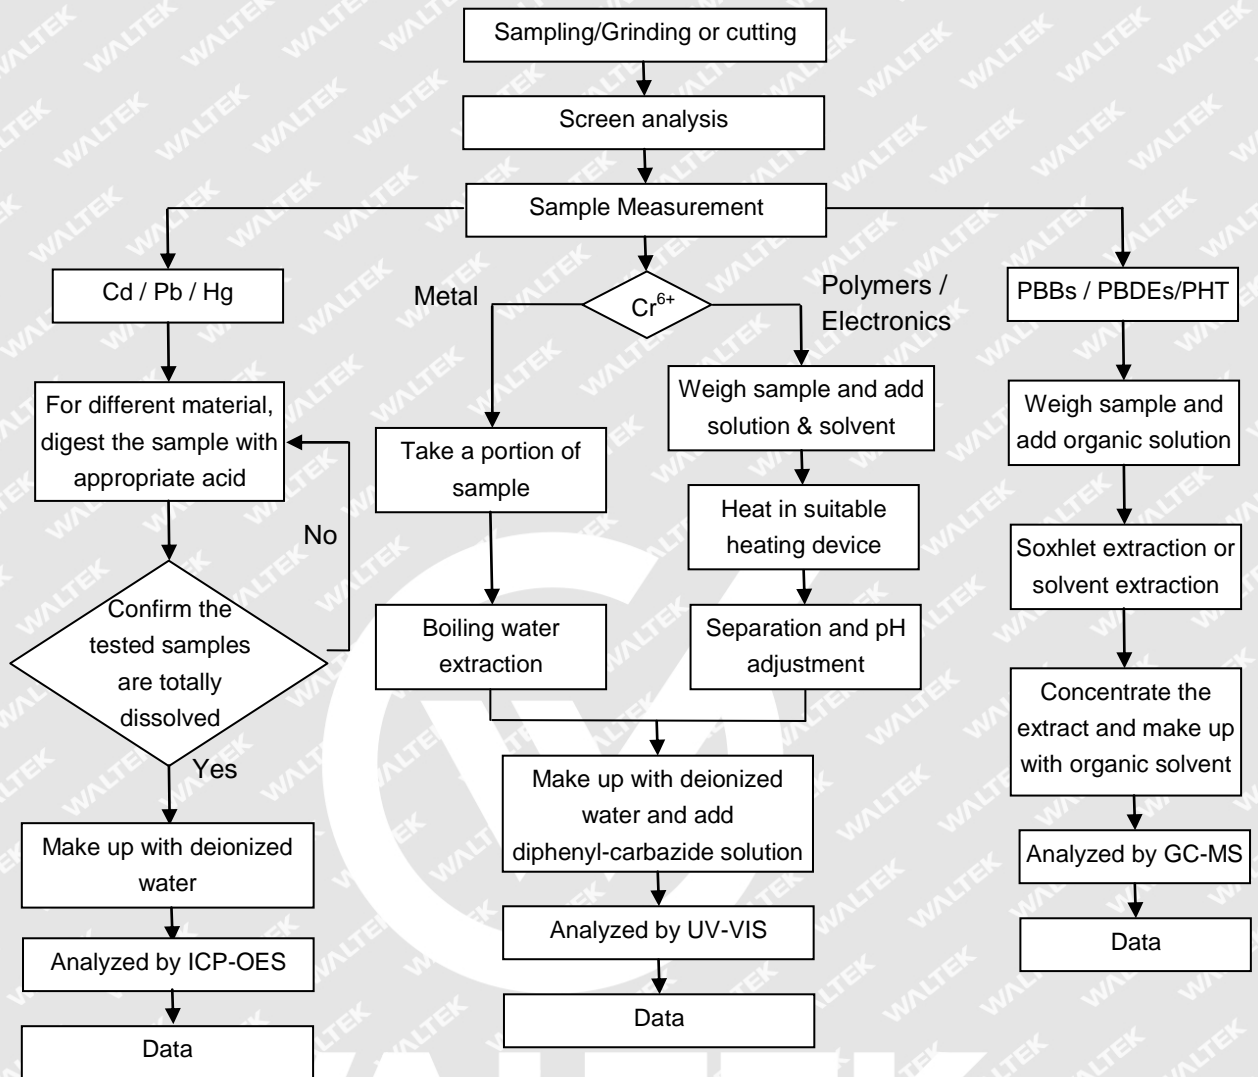







Sample Photo(s):


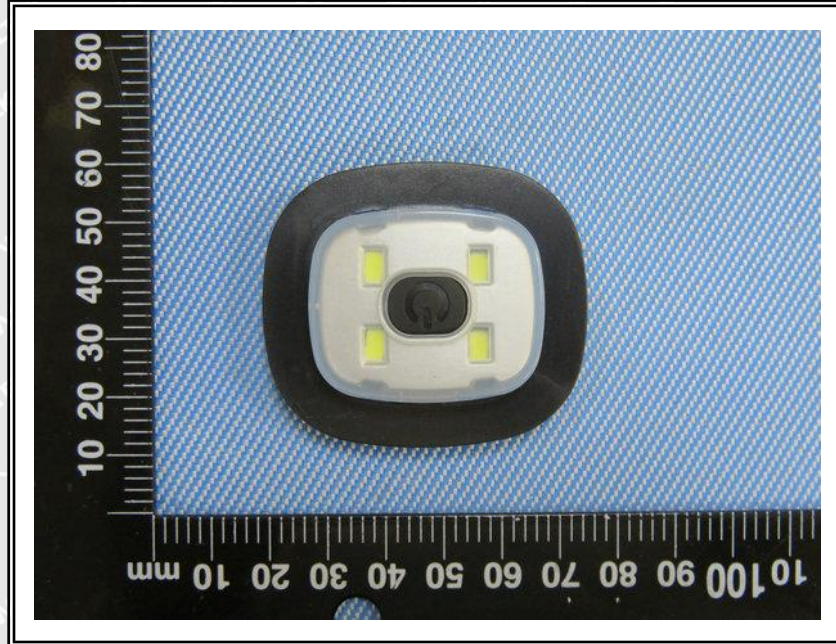




Photograph(s) of parts tested:

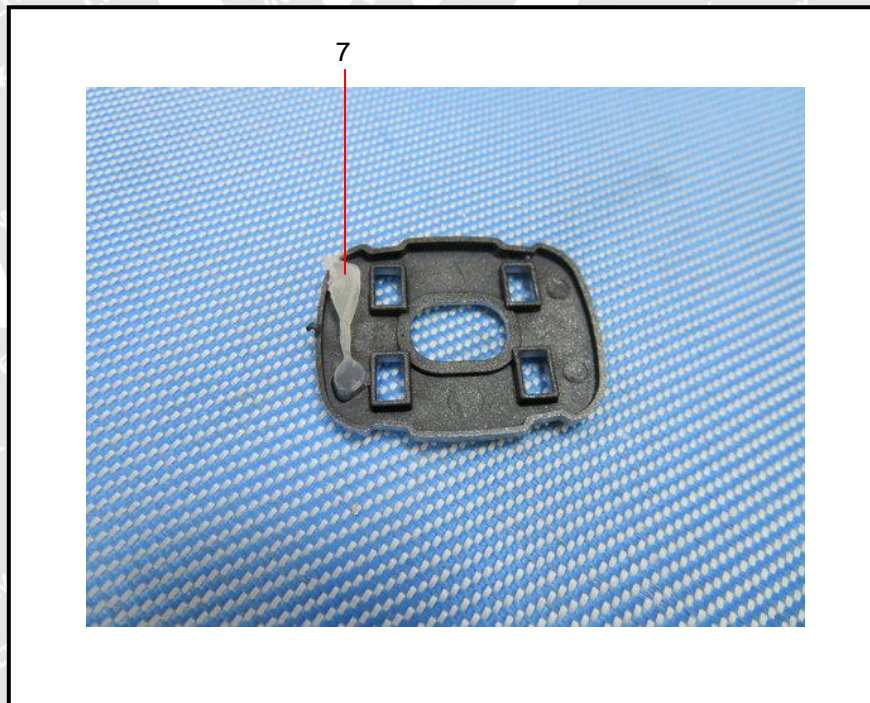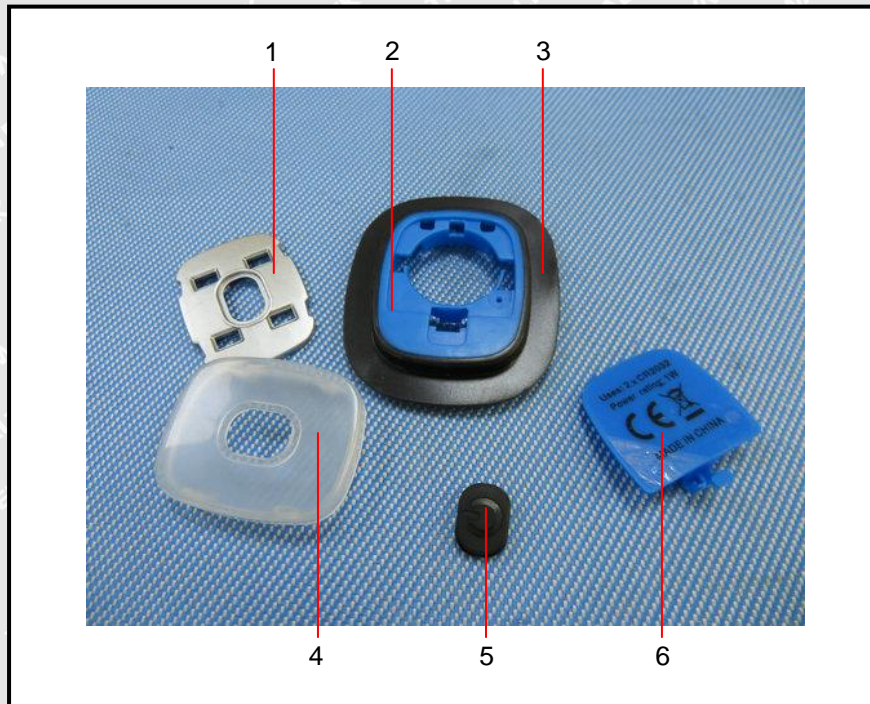

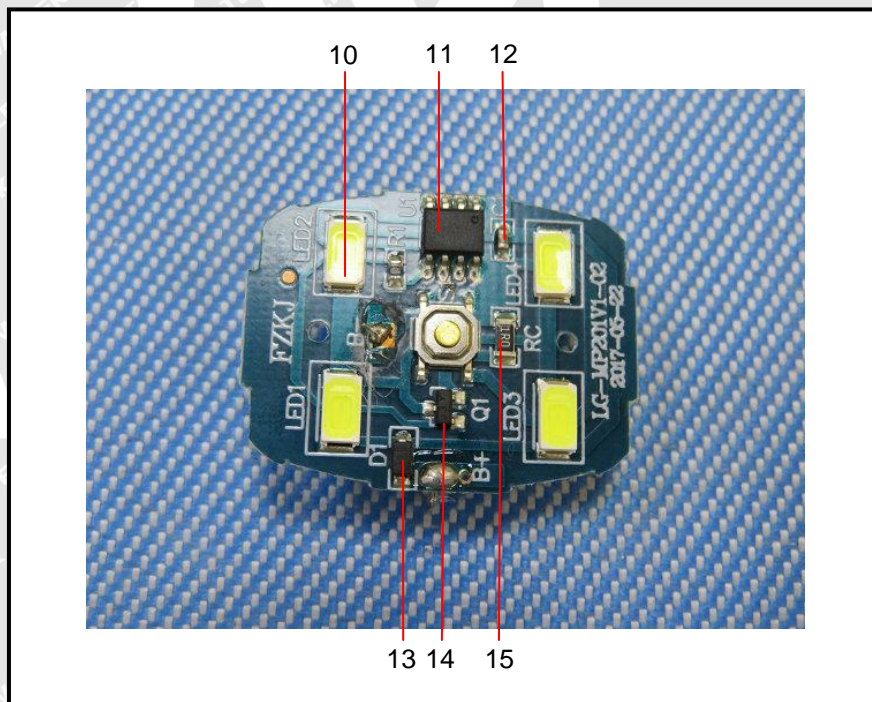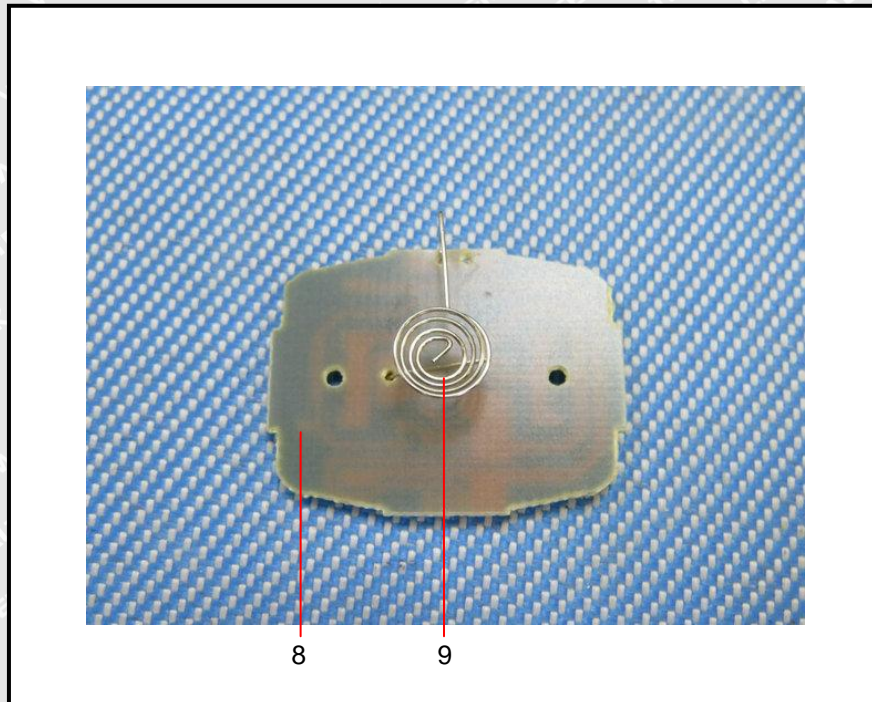

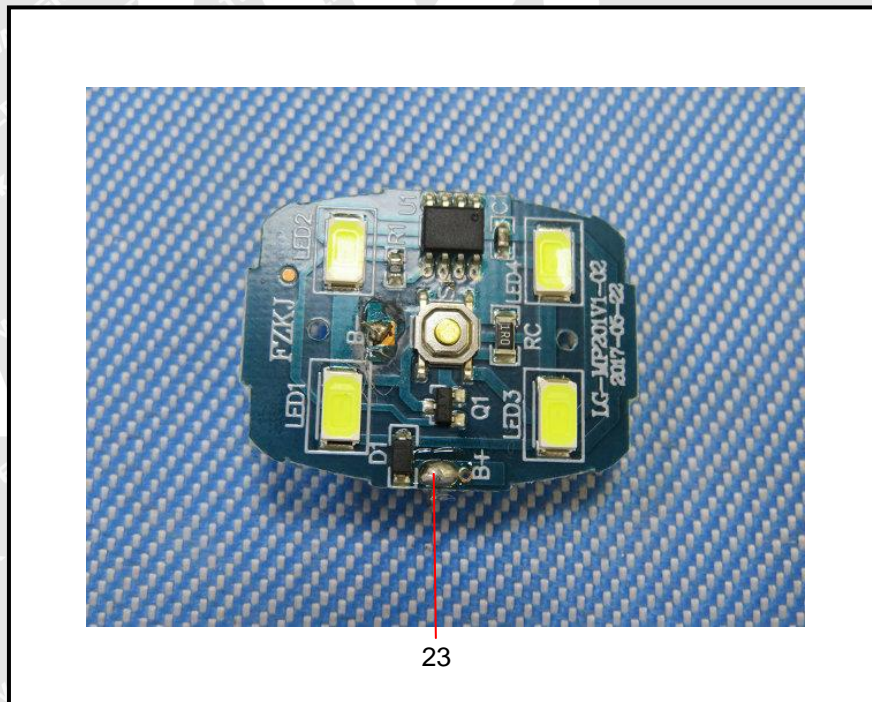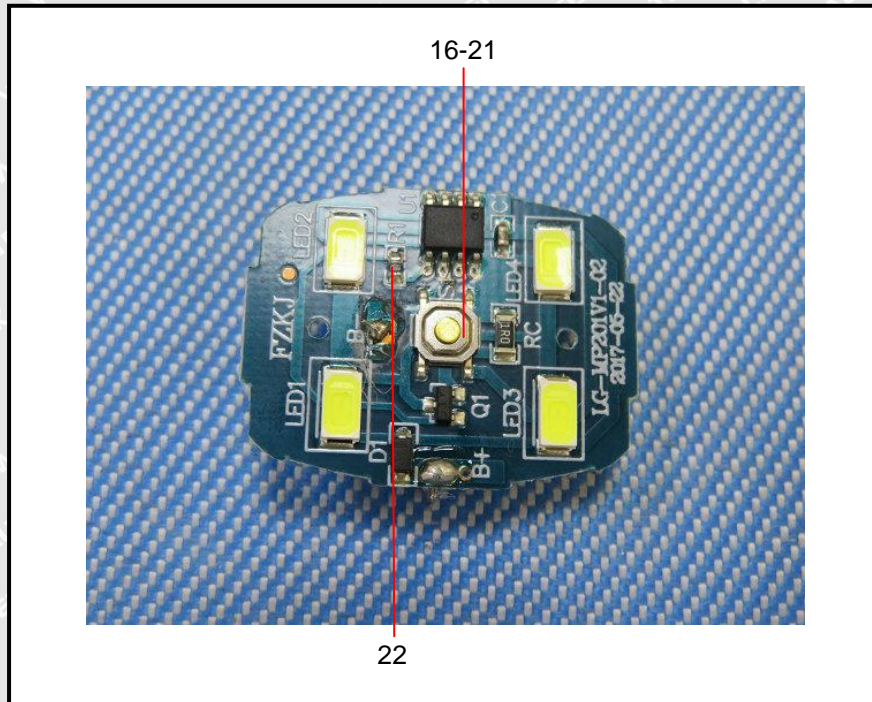

==== End of Report ====