



TEST REPORT

Reference No. : WTF20F09071164F
Applicant : Mid Ocean Brands B.V.
Address : 7/F., Kings Tower, 111 King Lam Street, Cheung Sha Wan, Kowloon, Hong Kong
Manufacturer : 114276
Sample Name : Stainless steel cutlery set
Model No. : MO6149
Test Requested : In accordance with Council of Europe Resolution CM/Res(2013)9 and Regulation (EC) No 1935/2004.
Test Conclusion : **Pass** (Please refer to next pages for details)
Date of Receipt sample : 2020-09-28
Date of Test : 2020-09-28 to 2020-10-10
Date of Issue : 2020-10-10
Test Result : Please refer to next page (s)

Remarks:

The results shown in this test report refer only to the sample(s) tested; this test report cannot be reproduced, except in full, without prior written permission of the company. The report would be invalid without specific stamp of test institute and the signatures of compiler and approver.

If the report is not stamped with the accreditation recognized seal, it will only be used for scientific research, education, and internal quality control activities, and is not used for the purpose of issuing supporting data to the society.

Prepared By:

Waltek Testing Group (Foshan) Co., Ltd.

Address: No.13-19, 2/F., 2nd Building, Sunlink International Machinery City, Chencun, Shunde District, Foshan, Guangdong, China

Tel:+86-757-23811398 Fax:+86-757-23811381 E-mail:info@waltek.com.cn

Compiled by:

Approved by:

Abby.Zhou

Abby.Zhou / Project Engineer

Dino Zhang

Dino.Zhang / Technical Manager

**Test Results:****Council of Europe Resolution CM/Res(2013)9-Specific Migration of Heavy Metal**

Test Items	1st+2nd Migration (mg/kg)		LOQ (mg/kg)	Limit (mg/kg)
	No.1	No.2		
Aluminium (Al)	ND	ND	0.2	35
Antimony (Sb)	ND	ND	0.02	0.28
Chromium (Cr)	ND	0.05	0.04	1.75
Cobalt (Co)	ND	ND	0.02	0.14
Copper (Cu)	ND	ND	0.2	28
Iron (Fe)	0.6	1.5	0.4	280
Manganese (Mn)	ND	ND	0.2	12.6
Molybdenum (Mo)	ND	ND	0.02	0.84
Nickel (Ni)	ND	0.18	0.02	0.98
Silver (Ag)	ND	ND	0.02	0.56
Tin (Sn)	ND	ND	0.2	700
Vanadium (V)	ND	ND	0.01	0.07
Zinc (Zn)	ND	ND	0.2	35
Arsenic (As)	ND	ND	0.002	0.014
Barium (Ba)	ND	ND	0.2	8.4
Beryllium (Be)	ND	ND	0.01	0.07
Cadmium (Cd)	ND	ND	0.002	0.035
Lead (Pb)	ND	ND	0.01	0.07
Lithium (Li)	ND	ND	0.01	0.336
Mercury (Hg)	ND	ND	0.002	0.021
Thallium (Tl)	ND	ND	0.0002	0.0007
Magnesium (Mg)	ND	ND	0.2	--
Titanium (Ti)	ND	ND	0.02	--




Test Items	3rd Migration (mg/kg)		LOQ (mg/kg)	Limit (mg/kg)
	No.1	No.2		
Aluminium (Al)	ND	ND	0.1	5
Antimony (Sb)	ND	ND	0.01	0.04
Chromium (Cr)	ND	ND	0.02	0.25
Cobalt (Co)	ND	ND	0.01	0.02
Copper (Cu)	ND	ND	0.1	4
Iron (Fe)	ND	ND	0.2	40
Manganese (Mn)	ND	ND	0.1	1.8
Molybdenum (Mo)	ND	ND	0.01	0.12
Nickel (Ni)	ND	ND	0.01	0.14
Silver (Ag)	ND	ND	0.01	0.08
Tin (Sn)	ND	ND	0.1	100
Vanadium (V)	ND	ND	0.005	0.01
Zinc (Zn)	ND	ND	0.1	5
Arsenic (As)	ND	ND	0.001	0.002
Barium (Ba)	ND	ND	0.1	1.2
Beryllium (Be)	ND	ND	0.005	0.01
Cadmium (Cd)	ND	ND	0.001	0.005
Lead (Pb)	ND	ND	0.005	0.01
Lithium (Li)	ND	ND	0.005	0.048
Mercury (Hg)	ND	ND	0.001	0.003
Thallium (Tl)	ND	ND	0.0001	0.0001
Magnesium (Mg)	ND	ND	0.1	--
Titanium (Ti)	ND	ND	0.01	--

Note:


1. Test Method: With reference to BS EN 13130-1: 2004, analysis was performed by ICP-OES and ICP-MS.
2. Test Condition and simulant: Sample(s) were migrated with 5g/L citric acid at 70°C for 1 hour.
3. "mg/kg" = milligram per kilogram of foodstuff in contact with
4. LOQ = Limit of quantitation
5. ND = Not Detected or lower than limit of quantitation
6. "--" = Not regulated
7. The specification was quoted from Technical Guide on Metals and alloys used in food contact materials of Council of Europe Resolution CM/Res(2013)9.




Sample Photo:

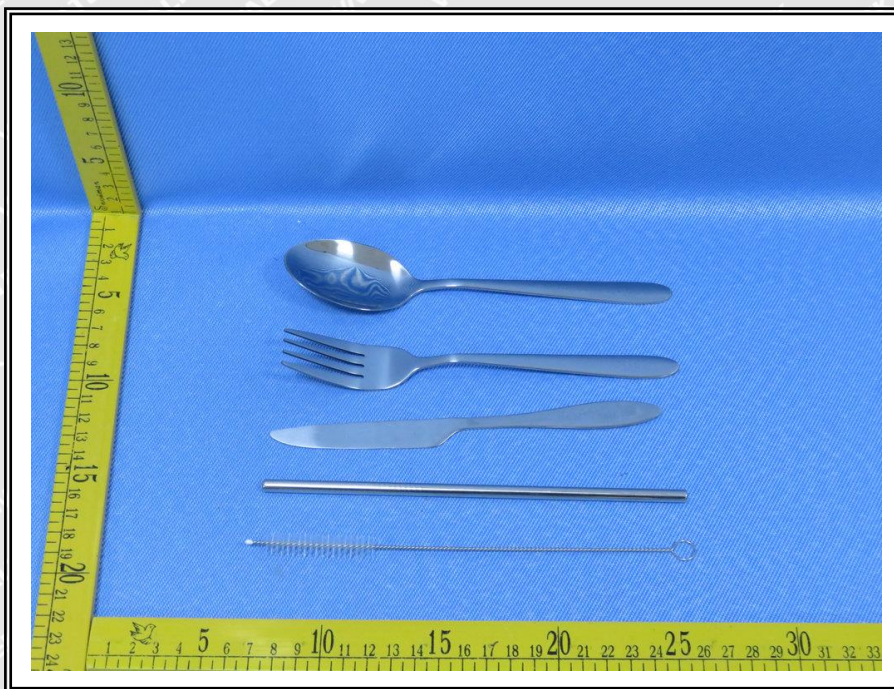


Photograph of parts tested:

No.	Photo of testing part	Parts Description	Client Claimed Material
1		Silvery metal	Stainless steel 430

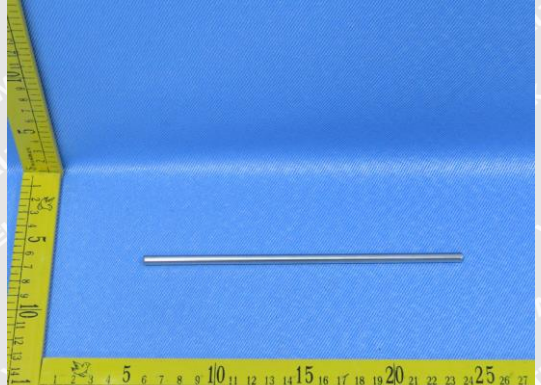

No.	Photo of testing part	Parts Description	Client Claimed Material
2		Silvery metal	Stainless steel 304

==== End of Report ====

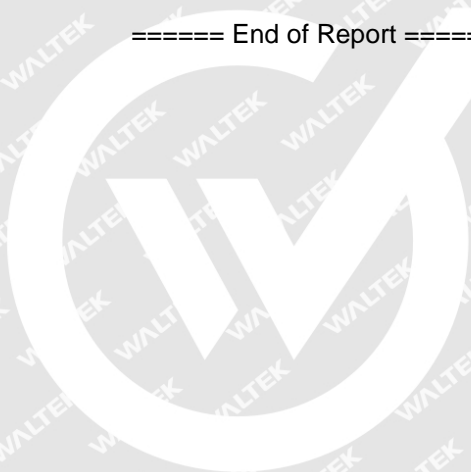

WALTEK

CO., LTD.